

Article

Recovery of Rare Earth Elements through Spent NdFeB Magnet Oxidation (First Part)

Srečko Stopić^{1,*}, Buse Polat¹, Hanwen Chung¹, Elif Emil-Kaya^{1,2,3}, Slavko Smiljanić⁴, Sebahattin Gürmen² and Bernd Friedrich¹

¹ IME Process Metallurgy and Metal Recycling, RWTH Aachen University, 52056 Aachen, Germany

² Department of Metallurgical & Materials Eng., Istanbul Technical University, 34469 Istanbul, Turkey

³ Department of Materials Science and Tech., Turkish-German University, 34820 Istanbul, Turkey

⁴ Faculty of Technology Zvornik, University of East Sarajevo, Karakaj 34A, 75400 Zvornik, Republic of Srpska, Bosnia and Herzegovina

* Correspondence: sstopic@ime-aachen.de; Tel.: +4917678261674

Abstract: Due to their remarkable magnetic properties, such as a high maximum energy product, high remanence, and high coercivity, NdFeB magnets are used in a variety of technological applications. Because of their very limited recycling, high numbers of spent NdFeB magnets are widely available in the market. In addition to China's monopoly on the supply of most rare earth elements, there is a need for the recovery of these critical metals, as their high import price poses an economic and environmental challenge for manufacturers. This paper proposes a pyrometallurgical recycling method for end-of-life NdFeB magnets by oxidizing them in air as first required step. The main goal of this method is to oxidize rare earth elements from NdFeB magnets in order to prepare them for the carbothermic reduction. The experimental conditions, such as the oxidation temperature and time, were studied in order to establish the phase transformation during oxidation using the Factsage Database and experimental conditions. Our thermogravimetric analysis TGA analysis revealed an increased sample mass by 35% between room temperature and 1100 °C, which is very close to the total calculated theoretical value of oxygen (36.8% for all elements, and only 3.6% for rare earth elements REE), confirming the complete oxidation of the material. The obtained quantitative analysis of the oxidation product, in (%), demonstrated values of 53.41 Fe₂O₃, 10.37 Fe₃O₄; 16.45 NdFeO₃; 0.45 Nd₂O₃, 1.28 Dy₂O₃, 1.07 Pr₂O₃, and 5.22 α-Fe.

Keywords: recycling; oxidation; rare earth elements; magnets

Citation: Stopić, S.; Polat, B.; Chung, H.; Emil-Kaya, E.; Smiljanić, S.; Gürmen, S.; Friedrich, B. Recovery of Rare Earth Elements through Spent NdFeB Magnet Oxidation (First Part). *Metals* **2022**, *12*, 1464. <https://doi.org/10.3390/met12091464>

Academic Editor: Petros Tsakiridis

Received: 18 July 2022

Accepted: 29 August 2022

Published: 31 August 2022

Publisher's Note: MDPI stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Copyright: © 2022 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<http://creativecommons.org/licenses/by/4.0/>).

1. Introduction

Rare earth elements (REE) are known as 'industrial vitamins', attracting high attention worldwide. Currently, REEs are vital components of many modern technologies, including electric and conventional cars, computers and smart phones, renewable energy infrastructure, and phosphor light [1–5]. Their unique properties, such as radiation emission and magnetism, allow for REEs to be used in many different therapeutic and diagnostic applications in modern medicine. During the last ten years, rare earth elements have attracted high attention in regard to their production. The production of rare earth elements has mostly been studied using different ores, concentrates, and slags worldwide [6–10]. The supply and demand of rare earth elements (REE) have been widely discussed and received large media coverage in recent years in contexts where these are used in high technological products and applications, such as electric vehicles and motor, generator, and energy production [11,12].

Because of higher demands in comparison to the real production of these materials, various studies by researchers from all fields have identified REEs to be critically scarce materials, directly or indirectly contributing to the global goal of a low-carbon energy

system. Among the critical materials, the roles of neodymium- and dysprosium-formed magnets, for instance, are crucial due to their outstanding magnetic properties that demonstrate their rich energy density compared to AlNiCo or ferrite magnets of the same dimensions. Due to this unique property, NdFeB magnets are among the strongest magnets used in technological applications, containing between 25–30 wt.% of REEs [13,14], proving their high value as an important secondary raw material source.

The recycling of NdFeB magnets often combines pyrometallurgical and hydrometallurgical treatment for optimal extraction, as seen in [15–20]. This paper focuses on the pyrometallurgical treatments that enable a high reaction rate and material throughput rate while maintaining a marketable selectivity. This was demonstrated by the high-REE-concentrated phase produced through the method used in this paper within 10 min of smelting. An upscaled study, however, could demonstrate several drawbacks, such as high investment and operational costs, along with the high-energy input and subsequent process used to improve the product quality. In the research field, however, plenty of different methods were studied with the similar aim of recovering and extracting remaining REEs from spent materials, particularly NdFeB magnets.

Murase et al. [15] investigated the recovery of metals from NdFeB magnet sludge. The authors utilized the method of chemical vapor transport along a temperature gradient. This method is based on the tendency of metal halides, including rare earth halides, to form halogen-bridged vapor complexes when reacted with other volatile metal halides, and the differences between the temperature dependences of the formation–decomposition equilibrium of the halogen complex. Using AlCl_3 as the metal halide complex former, magnets with the following composition were treated using the vapor transport technique:

The recovery process was conducted using an apparatus that contained two tubular electric furnaces, the first one for the AlCl_3 and the second for the magnet sludge. The temperature gradient was created by dividing the second tube into several heating zones. The magnets were heated to 1050 °C, N_2 and Cl_2 gas was streamed through the reactor as chlorinating agents, and the AlCl_3 was allowed to evaporate into its gaseous form, Al_2Cl_6 . Under these conditions, the metals reacted with the Cl_2 gas to form metal chloride and, subsequently, with the complex former. The complex gas phase was driven through the different temperature zones of the second tube, and it sublimed and decomposed based on its decomposition temperature. The authors reported that the recovered purity of RE-chloride was between 91–98 mol.%, with NdCl_3 being more concentrated in the fractions of a higher temperature [15].

Takeda et al. [16] investigated the extraction of rare earth elements from magnet waste by remelting the scrap together with fluoride flux, based on the phase equilibria of the $\text{Ln}_2\text{O}_3\text{-LnF-Li}_2\text{O-LiF}$ system (Ln corresponds to rare earth elements, such as Nd and Dy). In this novel process, the rare earth oxide REO in the magnet waste reacted with the RE-fluoride in the flux to produce RE-oxyfluoride, which then dissolved into the fluoride flux as an ionic form. Through molten salt electrolysis, the RE in the flux was converted into metallic form, and the flux returned to the extraction process.

The fluoride flux was prepared using 98% LiF, 99.99% NdF_3 , and 99.5% DyF_3 , which were fused in an iron crucible at 1200 °C for 3h. The experimental work was conducted by charging the fluoride flux and magnet waste in an iron crucible which was sealed by welding. The crucible was then heated inside a steel container with argon at 1230 °C for 12–78 h and then removed for analysis. The evaluation of the process was based on the oxygen content of the magnetic waste. The presence of oxyfluoride in the flux was confirmed by SEM-EDX analysis. In addition, neodymium oxyfluoride was identified by the XRD patterns. This confirmed that the Nd_2O_3 in the magnet was removed in the flux, with a maximum extraction ratio of 80–90%. The oxygen concentration of the alloy had decreased to 160 ppm from 5000 ppm due to the increase in the mass of the flux to 1.5 times the equivalent amount [6].

Nakamoto et al. [20] studied the separation of Fe and an oxide mixture of Nd, Dy, and Pr from the NdFeB magnetic sludge that arises from the magnet production. The authors' method utilized the difference in the oxygen affinity between the REE and Fe under the influence of carbon as a contact material for the reduction of Fe, demonstrating an efficient separation. Based on this theory, they investigated the phase separation efficacy at temperatures between 1300 and 1550 °C, as well as at holding times of 1, 3, 9, and 16 h. The authors first treated the magnetic sludge by heating to 300 °C and then washing with distilled water three times.

The samples were melted in an electric furnace at the respective temperatures and holding times. Carbon powders of approximately 3 wt.% were added to the mixture and, after the holding time, the samples were cooled using an Ar gas flow. The results showed that the oxide and iron phase were present at all the holding times. The chemical composition showed that the holding time of 3 h and 16 h yielded the highest purity of iron and the highest amount of REE oxides in the two phases. The temperature investigation was concluded at only 1550 °C, and the two phases were macroscopically separated. The authors noted an increased separation due to the addition of B₂O₃ and the influences of the viscosity and melting temperature of the oxide melts [20].

In a previous study conducted by Kruse et al. [21,22], NdFeB grinding slurries from the shaping process step in the production of sintered NdFeB magnets were treated by the pyrometallurgical method to recover REEs, focusing on Nd, Pr, and Dy. The raw materials contained a mixture of metallic swarf powders, abrasive media, and cooling agents. After removing the organic residues and cooling agents via pyrolysis thermal preconditioning, the authors melted the grinding slurry in a vacuum induction furnace and managed to separate the REEs from the iron by enriching them in a slag phase due to the high oxygen affinity of the REEs compared to the iron. Based on their results, pre-requisites for the separation are a minimum oxygen content of 7 wt.% and carbon content of 2 wt.%. The main goal of our work was to verify this strategy in order to produce concentrates of the rare earth elements.

Saito et al. [23] investigated the extraction of Nd from waste NdFeB magnets using the glass slag method. NdFeB master alloys were produced and melted in a boron nitride crucible along with pieces of boron trioxide fluxes. The alloy was oxidized through slow heating until it reached above the melting point of the flux and then cooled to room temperature in an argon atmosphere, resulting in the alloy being encapsulated in the boron trioxide. Owing to the strong affinity of RE with the flux, a reaction between NdFeB and the B₂O₃ took place during undercooling, which dissolved the Nd from the main matrix into Nd₂O₃ in the boron trioxide glass slag, leaving behind α -Fe and Fe₂B phases. A chemical analysis reported a change in the content of Nd in the boron trioxide phase from 0.01 wt.% to 25.80 wt.%. The master alloy, on the other hand, contained 95.86 wt.% Fe and 3.82 wt.% B after the glass slag treatment, demonstrating the ability of boron trioxide to remove Nd from NdFeB.

A similar improved method proposed and reported by Bian et al. [24] uses the FeO-B₂O₃ flux as a replacement of the B₂O₃ flux used by Saito et al. [23] in the selective reduction of Nd by FeO, due to its larger chemical potential compared to B₂O₃. Through the FeO-B₂O₃ flux, almost all of the REEs were extracted in the slag phase, while, simultaneously, the FeO was reduced entirely to metal phase. The authors reported a highest purity of more than 98.4 wt.% and an extraction ratio for the rare earth material of more than 99.5 wt.% at temperatures between 1673 K and 1823 K. This demonstrated that the FeO-B₂O₃ fluxes are better than pure Fe₂O₃ and B₂O₃.

Tanvar and Dhawan [25] investigated the recovery of REEs by a combined pyro- and hydrometallurgical method. The authors first applied microwave exposure-assisted carbothermic reduction to the end-of-life magnets and then conducted their recovery by acid leaching. In the experimental procedure, the crushed end-of-life magnets were exposed to microwaves under the stoichiometric addition of charcoal powder as a reducing agent. The exposure to the microwaves was reported to enable a rapid temperature increase from

room temperature to 990 °C within 1.2 min at a lower energy cost of 7.5 MW h/t, compared to the 1350 MW h/t cost using a muffle furnace. During the exposure, metallic Fe and Fe₂O₃ were formed with the liberation of the REO with an approximately 55% yield. The acid leaching recovery after the microwave carbothermic reduction exhibited an extraction rate of 40–60%, considering the excessive dissolution of Fe, which restricted the precipitation process. The final reported purity of the REO from the leaching and precipitation was 98%, showing that this is a promising method of carbothermic reduction and eventual hydrometallurgical treatment.

The method of carbothermic reduction is a widely applied technique due to its versatility. Based on the Ellingham diagram, REO can be directly reduced by either calcium [26] or carbon [27] at higher temperatures. The reduction of REO to metallic RE, however, is often coupled with the formation of high-melting RE-carbides that require the accurate selection of the temperature, CO/CO₂ ratio, and a low pressure up to vacuum conditions. The optimum combination of these parameters can usually be derived from an Ellingham diagram and the previously mentioned data [28–31], but due to the lack of thermodynamic data for REEs, it is often very difficult to conduct the carbothermic reduction of REO.

Yang et al [32] presented a critical review of methods of REE recovery from end-of-life NdFeB permanent magnet scrap, providing a list of efficient technologies that have been developed and implemented in practice.

Based at previously mentioned information, the research strategy used in this work is presented at Figure 1:

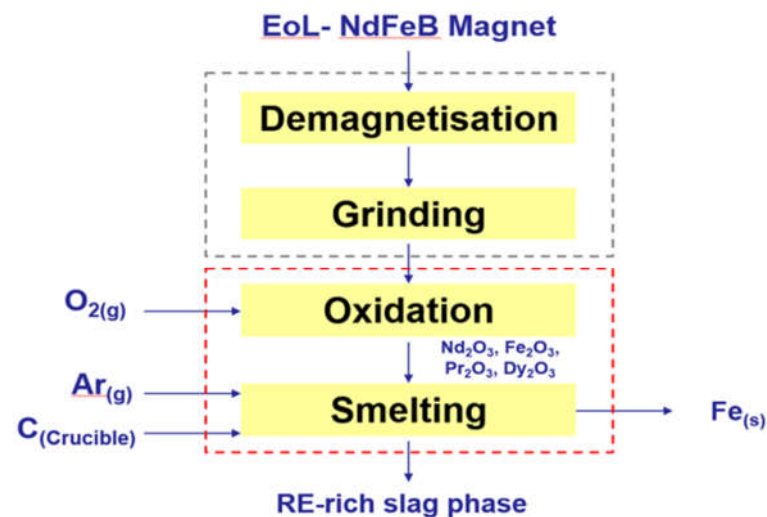


Figure 1. Proposed strategy for study in this work.

Because the literature study highlighted that the conversion methods of many researchers involve complex or difficult processes, our proposed pyrometallurgical method offers simple solutions. Obtaining rare earths from ores, which constitute a small percentage, is a highly complex and indiscriminate process. This is because the recycling of spent NdFeB-magnets has become a new motivation for the production of rare earth materials from secondary raw materials, which, as new raw materials used for treatments, are richer in rare earths than ores, which are insufficiently used in recycling, representing a serious environmental problem. In particular, in this work, we present the analysis of one pyrometallurgical method, which should be distinguished from the hydrometallurgical method in that it enabled a separation of iron and creates new concentrates of rare earth elements.



The method of ensuring the presence of oxygen in the magnet sample was applied in this study by first treating the samples with an oxidation step. The unconventional method of converting the magnets into an oxide form enables the utilization of the difference in the oxygen affinity between the REE and Fe phases. The main aim was to study the selectivity of the oxidation process concerning the rare earth elements iron and boron. We hypothesized that the oxidation step would lead to a suitable form for the subsequent carbothermal reductive process, which enables the separation of the rare earth elements boron and iron.

2. Thermochemical Analysis of the Oxidation

The analysis of the Gibbs energy required for the oxidation of metals at different temperatures assumes that mixed oxides will be formed, as shown with Equations (1)–(3):



M : Fe, Nd, Dy, B



Various phases during the oxidation of the mass sample were observed in previously mentioned literature ($NdFeO_3$, $PrFeO_3$, and Nd_2O_3). A diagram based on the thermochemical calculations was used to predict the possible phase formation and its corresponding sequence, and this is shown in Figure 2.

The figures demonstrate that the first phase to form was Nd_2O_3 , due to its mostly negative standard-free enthalpies of formation (ΔG^0), following by $NdFeO_3$ and finishing with Fe_2B , as the line of FeB is slightly above 0 in the figures, corresponding to a non-spontaneous reaction. Based on the composition of the raw materials, the phases of Nd_2O_3 , $NdFeO_3$, and Fe_xO_y were highly expected.

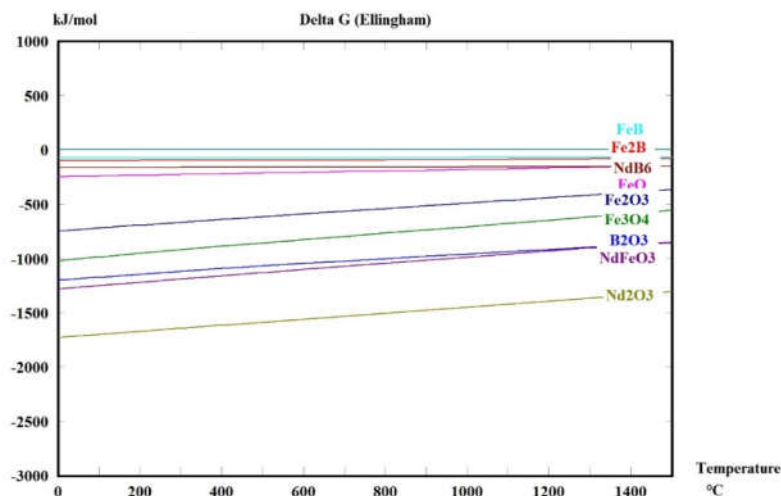


Figure 2. Phase formation during oxidation of the NdFeB magnets.

Due to the thermodynamics of metal oxidation, a widely used tool in the metallurgy field is the Richardson–Ellingham diagram, which plots the standard free enthalpies of formation for the reduction of metal oxides to metals against the temperature. The standard free enthalpies of formation in the equilibrium can be calculated according to Equation (4), under the assumption that the temperature dependence of ΔH and ΔS is negligible:

$$\Delta G^0 = \Delta H^0 - T\Delta S^0 = -RT \ln (k) \quad (4)$$

A pre-requisite for the reduction reaction to take place, according to the Richardson–Ellingham diagram, is that the metal must have a lower affinity for oxygen than the reducing agent. In other words, the ΔG^0 line of the target metal has to be above the ΔG^0 line of the reducing agent. Due to a lack of thermodynamic data, a simplification was adapted here, where the individual activities of each element in the multicomponent system were not considered. The Richardson–Ellingham diagram shows that the REEs had the highest affinity for oxygen in the pure substances. Unlike REEs, the iron had a much higher oxygen affinity and could be reduced using several elements, including carbon and aluminum.

3. Experimental Procedure

3.1. Materials and Methods

Spent magnets from the company Miknatis Ar-Ge, located in Istanbul, Turkey, were obtained and conditioned prior to the experimental phase. These were first demagnetized at 350 °C for 30 min and then milled into magnet powders. The samples were thermally treated by oxidizing in air and then smelted in a vacuum induction furnace (MiniVIM/Heraeus, Hanau, Germany) in an argon atmosphere. The phase analysis of the magnet powders was investigated by XRD (Bruker D8 Advance, Karlsruhe, Germany) analysis with a standard Cu wavelength of 1.5406 Å. The chemical analysis of the leachate obtained after the total dissolution of spent NdFeB magnets was conducted using ICP-OES (Spectro Arcos, SPECTRO Analytical Instruments GmbH, Kleve, Germany). The dynamic particle size analysis was conducted using a dynamic particle analyzer (Sympatech QuickPick Oasis with a M5 lens, software PAQXOS 4.1). The SEM analysis was performed using the JSM 7000F by JEOL (construction year 2006, JEOL Ltd., Tokyo, Japan) and the EDX analysis was performed using the Octane Plus-A by Ametek-EDAX (construction year, 2015, AMETEK Inc., Berwyn, PA, USA) with the software Genesis V 6.53 by Ametek-EDAX, Berwyn, PA, USA. The thermal gravimetric analysis (TGA, NETZSCH, Selb, Germany) was performed using the typical instrumentation and conditions.

The oxidation experiments were performed in a small tubular furnace, Thermostar, Aachen.

The chemical analysis of NdFeB powder revealed, in (%), 21.7 REE, 73.8 Fe, 0.66 B, and 0.0006 Ni, as shown in Table 1:

Table 1. Chemical analysis of the powder.

Sample NdFeB (%)	Nd	Ni	Fe	B	Pr	Dy
Weight (%)	15.9	0.0006	73.8	0.662	5.6	0.201

As shown in Table 2, the quantitative XRD analysis of the NdFeB powder identified the composition (%): 87.19 Nd₂FeB₁₄, 3.05 Pr₂FeB₁₄, 4.26 FeB₅, 2.04 DyF₅, and 2.46 DyF₂.

Table 2. Rietveld XRD quantitative analysis of the NdFeB magnets.

Phase	DyFe ₂	DyFe ₅	FeB ₅	Nd ₂ FeB ₁₄	Pr ₂ FeB ₁₄
Weight %	2.46	3.04	4.26	87.19	3.04

The particle size analysis of the powder revealed that 50% particles were about 39.85 µm. The smallest fraction amounted 7.35 µm in comparison to the largest fraction of 90.40 µm, as shown in Table 3.

Table 3. Particle size analysis of the NdFeB powders after demagnetizing, grinding, and sieving.

Samples (µm)	X ₃₀	X ₅₀	X ₉₀
NdFeB	7.35	39.85	90.40

The particle size distribution confirmed the presence of particles between 33.6 and 39.85 μm (about 50 % of particles in the structure), as shown in Figure 3.

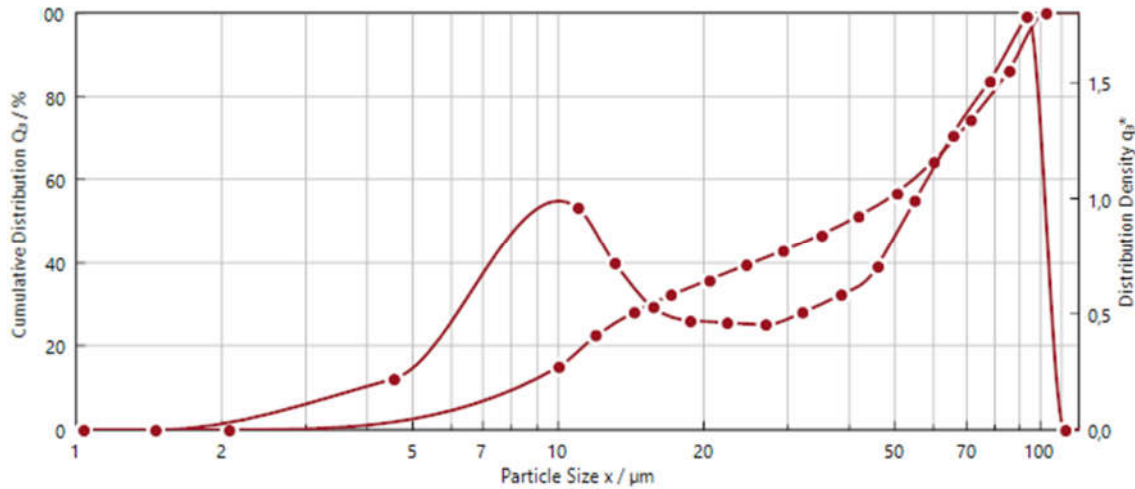


Figure 3. Dynamic particle analysis of the NdFeB magnet powders with the distribution sum (Q_3) and distribution density (q_3^*).

Figure 3 shows the cumulative distribution (Q_3) and distribution density (q_3^*) of the NdFeB powders with the diameter (EQPC) values of the powders. These results indicate that 90.3% of the pre-treated powder showed a size range of 1–90 μm , with a global maximum of $\sim 100 \mu\text{m}$.

The SEM Analysis confirmed the irregular round agglomerated particles of the spent magnets, as shown in Figure 4.

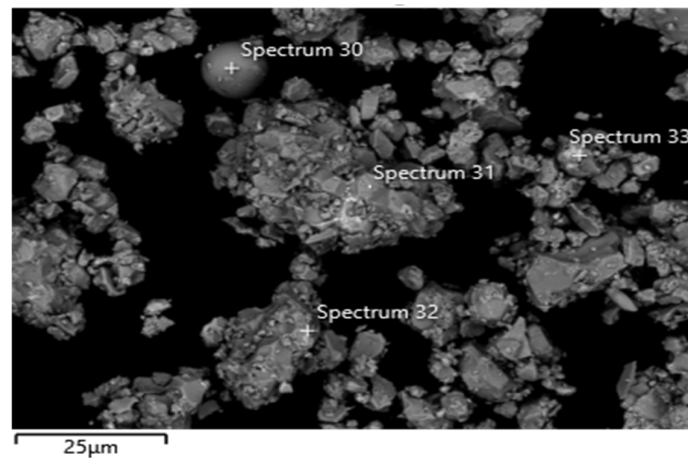


Figure 4. SEM analysis of the NdFeB magnets with places of the EDX Analysis (Spectrum 30, Spectrum 31, Spectrum 32 and Spectrum 33).

3.2. Results and Discussion

The results refer to thermalgravimetric and differential thermal analysis, along with the study of the isothermal oxidation of the NdFeB spent magnets, as first steps used in this study to investigate the oxidation.

3.2.1. Differential Thermal (DTA) and Thermalgravimetric Analysis (TGA)

DTA and TGA analyses were used to measure, respectively, the temperature difference between the NdFeB and inert reference sample as a function of the temperatures between 25 °C and 1100 °C in air, and the weight change of the samples as a function of the temperature while subjected to a controlled heating program, as shown in Figure 5.

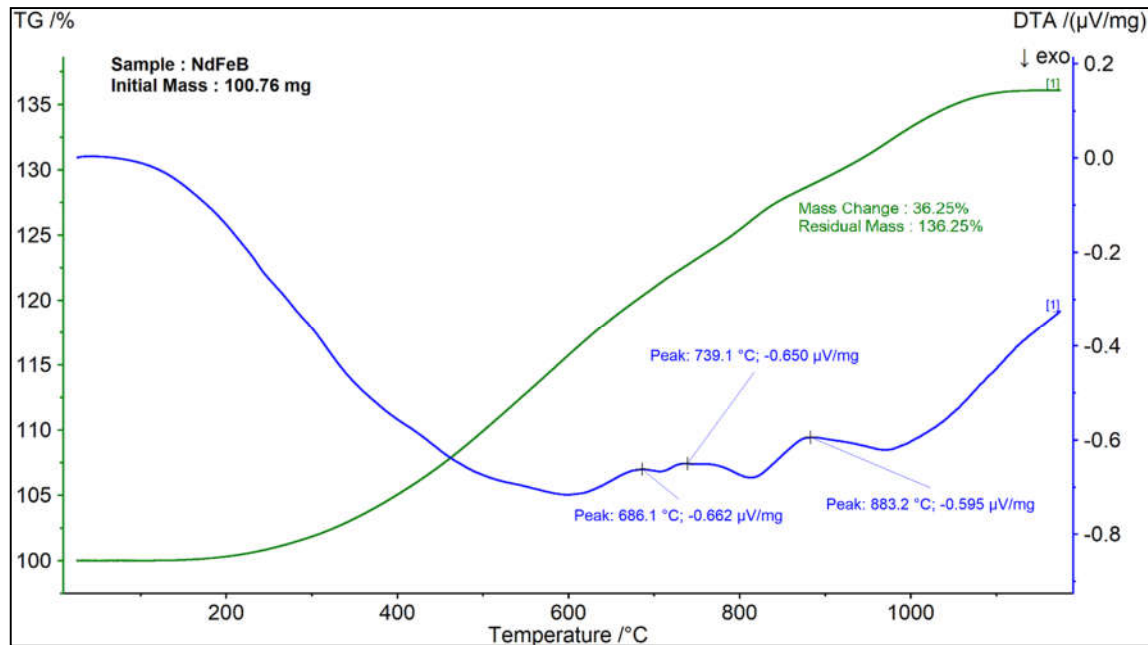


Figure 5. DTA/TGA analysis of the NdFeB magnets in air (10 K/min).

Because of the oxidation process, the TGA analysis revealed an increased sample mass by about 35% between room temperature and 1100°C, which is very close to the total calculated theoretical value (36.8%) of the oxidation of Fe, REE, and B. The calculated theoretical value of the oxidation of REE amounts to 3.6%. The DTA analysis revealed three peaks at 688.1, 739.1, and 883, 2 °C, respectively, which means that three different types of oxides were formed. We assumed that iron oxide, REE oxides, and boron oxide would be formed in the absence of a selective oxidation. The obtained results confirmed that this oxidation was not selective at this chosen interval.

3.2.2. Oxidation of Particles in the Furnace

According to the previously mentioned DTA and TGA data, the starting oxidation was performed in furnace with a small quantity of material (1 g) at temperatures between 500°C and 1100°C for 13, 30, 45, 60, 75 and 90 min in order to select the parameters for the oxidation of 1 kg of spent material required for the smelting process. The obtained results are shown in Table 4.

Table 4. Increased mass (g) during oxidation between 500 °C and 1100 °C.

Time (min)	500 °C	600 °C	700 °C	800 °C	900 °C	1000 °C	1100 °C
15	0.118	0.05	0.214	0.244	0.238	0.264	0.274
30	0.134	0.192	0.242	0.294	0.251	0.293	0.287
45	0.161	0.221	0.248	0.299	0.283	0.336	0.295
60	0.178	0.206	0.276	0.299	0.327	0.333	0.337
75	0.17	0.22	0.268	0.312	0.336	0.325	0.318
90	0.186	0.249	0.295	0.327	0.329	0.342	0.341

An increase in the temperature between 500 °C and 1100 °C over 15 and 45 min increased the mass of the initial sample. The maximum oxidation yield was obtained through a comparison with the theoretical oxidation value of 93% at the temperature of 1000 °C ($0.342/0.368 = 0.93$). Because the oxidation was complete, an increase in the temperature above 1000 °C did not significantly increase the oxidation efficiency of the spent NdFeB magnets.

The oxidation of 1 kg of the spent NdFeB magnets was performed at 1000 °C over 2 h in order to prepare the sample for the reductive smelting in the graphite crucible. The actual oxidation of the bulk magnet samples showed less mass change than the recorded results from the DTA/TG, i.e., incomplete oxidation. The final mass change produced by the oxidation was 27.2 wt.%, while the corresponding degree of oxidation of the mass sample was 78%. A qualitative X-ray diffraction analysis (XRD analysis) was conducted on the oxidized sample to determine the formed oxide phases and the results.

According to the XRD analysis, the oxidized material did not consist entirely of metal oxides. Through the oxidation, the majority of Nd₂Fe₁₄B was decomposed to form Fe oxides, Nd₂O₃ and NdFeO₃, as shown in Table 5.

Table 5. XRD analysis of the oxidized NdFeB samples.

Phase	Dy ₂ O ₃	FeB ₂	Fe ₂ O ₃	Fe ₃ O ₄	NdBO ₃	NdFeO ₃	Nd ₂ O ₃	α-Fe	Pr ₂ O ₃
Weight %	1.28	1.75	53.41	10.37	10.01	16.45	0.45	5.22	1.07

The obtained quantitative analysis identified a composition, in (%), of 53.41 Fe₂O₃, 10.37 Fe₃O₄, 16.45 NdFeO₃, 0.45 Nd₂O₃, 1.28 Dy₂O₃, 1.07 Pr₂O₃, and 5.22 α-Fe. The presence of boron in 10.01% NdBO₃ was in agreement with the 0.668 % boron present in the structure based on our comparison. We assumed that a small amount of NdBO₃ would cover the highly expected Pr₂O₃ or PrFeO₃, which were not detected in the structure. The presence of alfa ferrite was not expected in the oxidized structure, but could be separated by reductive smelting at a higher temperature. The oxidized structure is shown in Figure 6.

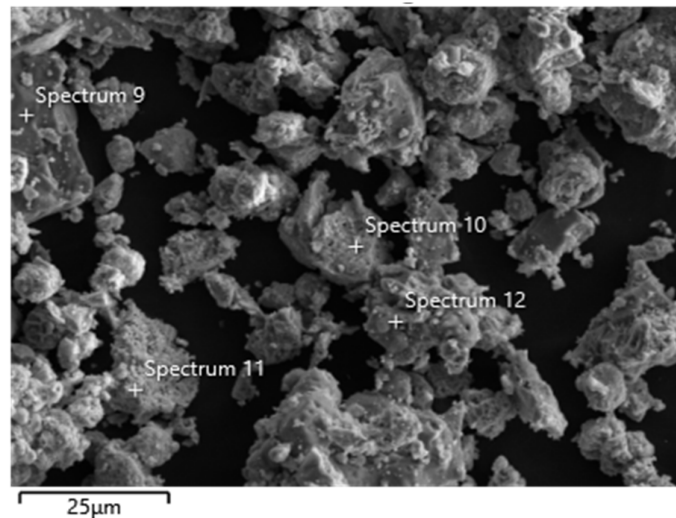


Figure 6. SEM analysis of the oxidized particles at 1000 °C with places of the EDX Analysis (Spectrum 9, Spectrum 10, Spectrum 11 and Spectrum 12).

The SEM analysis revealed very small round particles with irregular bigger particles in the structure. The EDX analysis confirmed that some particles were enriched with iron oxide.

As shown in Figures 7 and 8, the elemental analysis of spectra 9 and 10 showed a mixture of particles of Fe and rare earth elements with oxygen, which confirms the formation of metal oxides. In particular, some particles after oxidation contained mostly iron oxide, as shown in Figure 7.

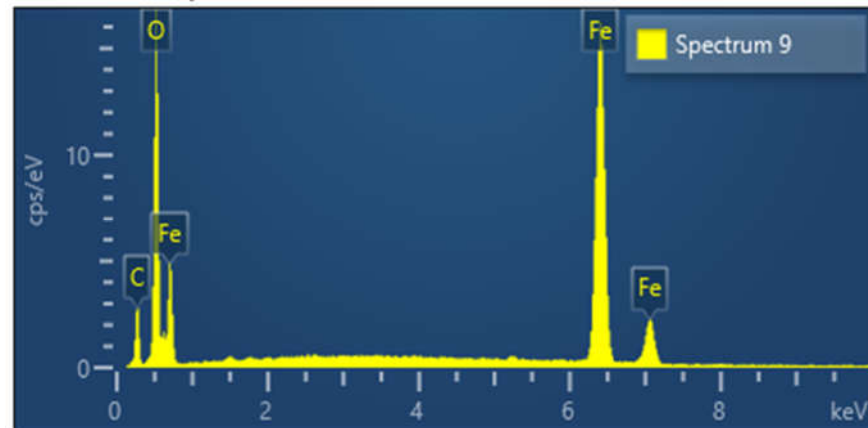


Figure 7. EDX analysis of certain particles after oxidation, containing mostly iron oxide (spectrum 9).

The analysis of spectrum 10 confirmed the presence of rare earth elements with iron and oxygen, as shown in Figure 8. All elements contained in the spent NdFeB magnets were oxidized.

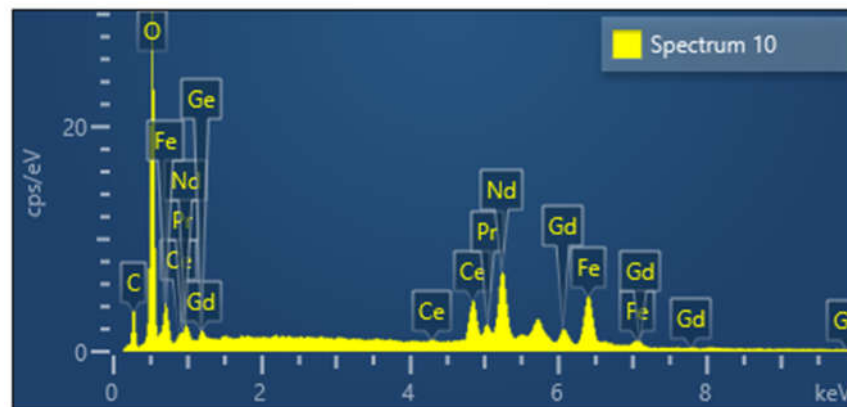


Figure 8. EDX analysis of the particles after oxidation (spectrum 10).

4. Conclusions

The literature study highlighted that the conversion methods used by many researchers involve complex or difficult processes. The study of Nakamoto and Kruse, related to fine magnet sludge with particle sizes much smaller than actual spent magnets, was successfully tested and validated during oxidation. All of the aforementioned shortcomings confirmed that our use of a simple, industrial, applicable oxidation method was correctly chosen.

In this proposed method, the materials are left to oxidize in air inside a laboratory-scale muffle furnace. This method could, theoretically, be transferred to the industrial scale, for example, in a tunnel furnace supplemented with a conveyer belt, or in a rotary kiln furnace that could promote the homogenous oxidation of the bulk materials.

In this study, a research methodology used for recycling end-of-life NdFeB magnets was investigated. The final aim of the work was to recover REEs by means of pyrometallurgical smelting, separating the magnets into a metal phase and a RE oxide-rich slag

phase. Our first step was to study the oxidation of spent NdFeB magnets as the preparation for the second phase, a reductive smelting process. The obtained results confirmed that the maximal oxidation was obtained at 1000 °C for 45 min.

XRD analyses were conducted for both phases, and the results showed that the REEs were in form of metal oxides, such as Dy₂O₃, Pr₂O₃, NdFeO₃, Nd₂O₃, and NdFeO₃. Boron was present in form of NdBO₃ and FeB₂. Iron was oxidized in form of Fe₂O₃ and Fe₃O₄. A total of 5.11% of iron was identified in form of α -iron and iron oxide. Outlooks of this work relate to the process optimizing, treatment, and recovery of the RE oxide-rich slag, and the identification of the limits of the carbothermic reduction. The results obtained here could be applied in further laboratory-scale studies and aid in the development of a sustainable economy.

Author Contributions: Conceptualization, S.S. (Srecko Stopic) and E.E.-K.; methodology, H.C.; software, H.C.; validation, S.S. (Slavko Smiljanic), E.E.-K., and B.P.; formal analysis, S.G.; investigation, H.C. and B.P.; resources, S.S. (Slavko Smiljanic) data curation, E.E.-K.; writing—original draft preparation, (Srecko Stopic) and H.C.; writing—review and editing, (Srecko Stopic); visualization, H.C.; supervision, S.G.; project administration, H.C.; funding acquisition, S.G. and B.F. All authors have read and agreed to the published version of the manuscript.

Funding: This research was funded by the Federal Ministry for Economic Affairs and Climate Action, grant number 273 EN. The APC was funded by the project “sustainable recovery of rare earth elements (Nd, Pr, Dy) from spent magnets.”

Institutional Review Board Statement: Not applicable.

Informed Consent Statement: Not applicable.

Data Availability Statement: Not applicable.

Acknowledgments: We would like to thank to the company Miknatis Ar-Ge in Istanbul, Turkey, for the provision of the spent NdFeB magnets.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Thomas, P.J.; Carpenter, D.; Boutin, C.; Allison, J.E. Rare earth elements (REEs): Effects on germination and growth of selected crop and native plant species. *Chemosphere* **2013**, *96*, 57–66.
2. Morais, C.; Ciminelli, V. Process development for the recovery of high-grade lanthanum by solvent extraction. *Hydrometallurgy* **2004**, *73*, 237–244.
3. Maestro, P.; Huguenin, D. Industrial applications of rare earths: Which way for the end of the century? *J. Alloys Compd.* **1995**, *225*, 520–528.
4. Krishnamurthy, N.; Gupta, C.K. *The Rare Earths, Extractive Metallurgy of Rare Earths*; CRC Press: Boca Raton, FL, USA, 2015; pp. 1–84.
5. Hoshino, M.; Sanematsu, K.; Watanabe, Y. REE mineralogy and resources. In *Handbook on the Physics and Chemistry of Rare Earths*; Elsevier: New York, NY, USA, 2016; Volume 49, pp. 129–291.
6. Davris, P.; Stopic, S.; Balomenos, E.; Pnias, D.; Paspaliaris, I.; Friedrich, B. Leaching of rare earth elements from Eudialyte concentrate by suppressing silicon dissolution. *Miner. Eng.* **2017**, *108*, 115–122.
7. Ma, Y.; Stopic, S.; Gronen, L.; Milivojevic, M.; Obradovic, S.; Friedrich, B. Neural Network Modeling for the Extraction of Rare Earth Elements from Eudialyte Concentrate by Dry Digestion and Leaching. *Metals* **2018**, *8*, 267.
8. Ma, Y.; Stopic, S.; Friedrich, B. Hydrometallurgical Treatment of an Eudialyte Concentrate for Preparation of Rare Earth Carbonate. *Johns. Matthey Technol. Rev.* **2019**, *63*, 2–13.
9. Yun, Y.; Stopic, S.; Friedrich, B. Valorization of Rare Earth Elements from a Steenstrupine Concentrate Via a Combined Hydrometallurgical and Pyrometallurgical Method. *Minerals* **2020**, *10*, 248.
10. Kilicarslan, A.; Voßenkaul, D.; Stoltz, S.; Stopic, S.; Nezihi, M.; Friedrich, B. Selectivity Potential of Ionic Liquids for Metal Extraction from Rare Earth containing Slags—A QEMSCAN assisted approach. *Hydrometallurgy* **2017**, *169*, 59–67.
11. Buchert, M.; Manhart, A.; Sutter, J. Untersuchung zu Seltenen Erden: Permanentmagnete im industriellen Einsatz in Baden-Württemberg. Studie im Auftrag des Ministeriums für Umwelt, Klima und Energiewirtschaft Baden-Württemberg. *Forum 6: Energieeffiziente Industrielle Antriebe und deren Abhängigkeit von Selten Erden*; p. 46. 2014. Available online: <http://www.oeko.de/oekodoc/2053/2014-630-de.pdf> (accessed on January 2014).

12. Ma, Y.; Stopic, S.; Friedrich, B. (2019), Hydrometallurgical Treatment of a Eudialyte Concentrate for Preparation of Rare Earth Carbonate, Johnson Matthey Technology Review, 63 (1) 2-13
13. Umweltbundesamt. Seltene Erden in Permanentmagneten. In *Für Mensch und Umwelt-Factsheet*; Umweltbundesamt: Dessau-Roßlau, Germany, 2019; pp. 1–10.
14. Sprecher, B.; Xiao, Y.; Walton, A.; Speight, J.; Harris, R.; Kleijn, R.; Visser, G.; Kramer, G.J. Life cycle inventory of the production of rare earths and the subsequent production of NdFeB rare earth permanent magnets. *Environ. Sci. Technol.* **2014**, *48*, 3951–3958. <https://doi.org/10.1021/es404596q>.
15. KMurase, K.; Machida, K.-I.; Adachi, G.-Y. Recovery of rare metals from scrap of rare earth intermetallic material by chemical vapour transport. *J. Alloy. Compd.* **1995**, *217*, 218–225, doi:10.1016/0925-8388(94)01316-A.
16. Takeda, O.; Nakano, K.; Sato, Y. Recycling of rare earth magnet waste by removing rare earth oxide with molten fluoride. *Mater. Trans.* **2014**, *55*, 334–341.
17. Kaya, E.; Kaya, O.; Stopic, S.; Gürmen, S.; Friedrich, B. NdFeB magnets recycling process: An alternative method to produce mixed rare earth oxide from Scrap NdFeB magnets. *Metals* **2021**, *11*, 716, doi:10.3390/met11050716.
18. Shirayama, S.; Okabe, T.H. Selective Extraction and Recovery of Nd and Dy from Nd-Fe-B Magnet Scrap by Utilizing Molten MgCl₂. *Metall. Mater. Trans. B Process Metall. Mater. Processing Sci.* **2018**, *49*, 1067–1077, doi:10.1007/s11663-018-1176-0.
19. Lyman, J.; Palmer, G. Recycling of Rare Earths and Iron from NdFeB Magnet Scrap. *High Temp. Mater. Process.* **1993**, *11*, 175–188.
20. Nakamoto, M.; Kubo, K.; Katayama, Y.; Tanaka, T.; Yamamoto, T. Extraction of rare earth elements as oxides from a neodymium magnetic sludge. *Metall. Mater. Trans. B Process Metall. Mater. Processing Sci.* **2012**, *43*, 468–476, doi:10.1007/s11663-011-9618-y.
21. Kruse, S.; Raulf, K.; Pretz, T.; Friedrich, B. Influencing Factors on the Melting Characteristics of NdFeB-Based Production Wastes for the Recovery of Rare Earth Compounds. *J. Sustain. Met.* **2016**, *3*, 168–178, doi:10.1007/s40831-016-0093-1.
22. Kruse, S.; Raulf, K.; Trentmann, A.; Pretz, T.; Friedrich, B. Processing of Grinding Slurries Arising from NdFeB Magnet Production. *Chem. Ing. Tech.* **2015**, *87*, 1589–1598, doi:10.1002/cite.201500070.
23. Saito, T.; Sato, H.; Ozawa, S.; Yu, J.; Motegi, T. The extraction of Nd from waste Nd–Fe–B alloys by the glass slag method. *J. Alloy. Compd.* **2003**, *353*, 189–193.
24. Bian, Y.; Guo, S.; Jiang, L.; Tang, K.; Ding, W. Extraction of Rare Earth Elements from Permanent Magnet Scraps by FeO–B₂O₃ Flux Treatment. *J. Sustain. Met.* **2015**, *1*, 151–160, doi:10.1007/s40831-015-0009-5.
25. Tanvar, H.; Dhawan, N. Microwave-Assisted Carbothermic Reduction of Discarded Rare Earth Magnets for Recovery of Neodymium and Iron Values. *JOM* **2020**, *73*, 54–62, doi:10.1007/s11837-020-04409-9.
26. Sharma, R.A. Neodymium Production Processes. *JOM* **1987**, *39*, 33–37. <https://doi.org/10.1007/BF03259468>.
27. Gupta, C.K.; Krishnamurthy, N. Oxide reduction processes in the preparation of rare-earth metals. *Min. Met. Explor.* **2013**, *30*, 38–44.
28. Ernst, S. *Chemische Technik (Winnacker-Küchler)*. Band 3: Anorganische Grundstoffe, Zwischenprodukte. Herausgegeben von Roland Dittmeyer, Wilhelm Keim, Gerhard Kreysa und Alfred Oberholz. *Angew. Chem.* **2006**, *118*, 29–30, doi:10.1002/ange.200585324.
29. Mendiara, T.; Jensen, A.; Glarborg, P. *Chemical Looping Reforming of Generator Gas*; CHEC Report No. R1001; 2010., Technical University of Denmark, Lyngby, Denmark
30. Frohberg, M.G. *Thermodynamik für Werkstoffingenieure und Metallurgen*; Wiley-VCH: Weinheim, Germany, 1994; ISBN: 978-3-527-30922-1.
31. Xie, W.H.; Huang, R.; Zhang, J.Z.; Li, W.; Yang, Y. Study on the interaction of rare earth element neodymium, iron and arsenic at 1173 K. *Gongneng Cailiao/J. Funct. Mater.* **2018**, *49*, 1134–1138, doi:10.3969/j.issn.1001-9731.2018.01.025.
32. Yang, Y.; Walton, A.; Sheridan, R.; Güth, K.; Gauß, R.; Gutfleisch, O.; Buchert, M.; Steenari, B.-M.; Van Gerven, T.; Jones, P.T.; et al. REE Recovery from End-of-Life NdFeB Permanent Magnet Scrap: A Critical Review. *J. Sustain. Met.* **2017**, *3*, 122–149.